



Technical Information: A2 ESR

A2 ESR IS AN AIR HARDENING COLD WORK TOOL STEEL

A2 ESR IS CHARACTERIZED BY MODERATE WEAR RESISTANCE COMBINED WITH GOOD TOUGHNESS

A2 ESR IS USED AS AN UPGRADE TO CONVENTIONAL A2


A2 ESR WILL HAVE HIGHER TOUGHNESS AND BETTER CLEANLINESS THAN STANDARD A2

TYPICAL CHEMICAL COMPOSITION

CARBON	1.00%	CHROMIUM	5.25%
MOLYBDENUM	1.10%	SILICON	0.35%
VANADIUM	0.25%	MANGANESE	0.85%

SBSM TOOL STEEL PROPERTIES COMPARISON

■ Relative Wear Resistance ■ Chipping Resistance

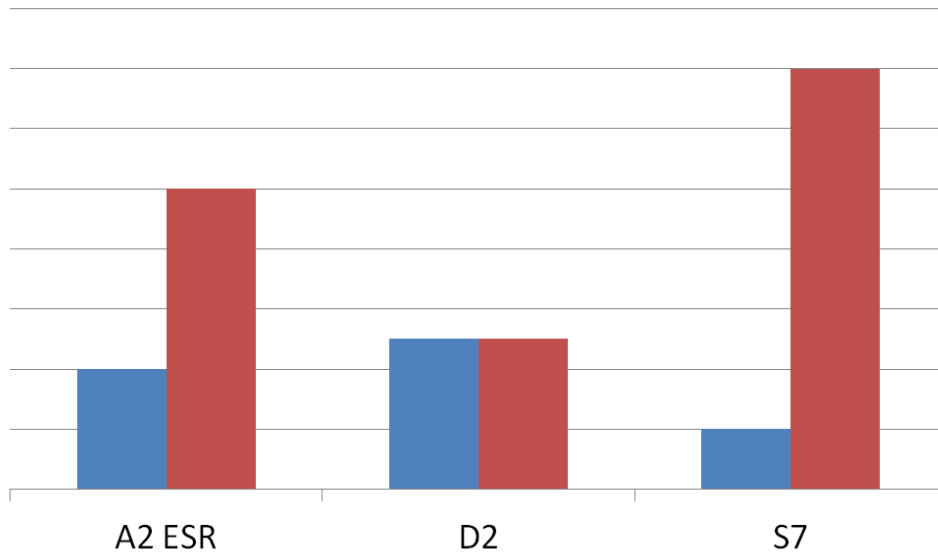

PHYSICAL PROPERTIES

MODULUS OF ELASTICITY.....30 PSI X 10⁶(207 GPa)
 DENSITY..... 0.283 LB/IN³
 ANNEALED HARDNESS.....210-225 BRINELL HARDNESS (BHN)



Technical Information: A2 ESR

HEAT TREATMENT

ANNEALING

HEAT TO 1600°F, HOLD TWO HOURS
SLOW COOL 20°F/HOUR TO 900°F
THEN AIR OR FURNACE COOL TO ROOM TEMPERATURE

STRESS RELIEVING

PERFORMED PRIOR OR AFTER MACHINING TO MINIMIZE DISTORTION IN HEAT TREATING
1100/1200°F, HOLD TWO HOURS
THEN AIR COOL TO ROOM TEMPERATURE

HARDENING

SALT BATH, PROTECTIVE ATMOSPHERE, OR VACUUM FURNACE EQUIPMENT PREFERRED.

HIGH HEAT (AUSTENITIZING)

1775°F FOR 30 MINUTES AT HEAT.

QUENCH

SALT BATH QUENCH TO 1000-1100°F, EQUALIZE, THEN AIR COOL TO 150°F .
VACUUM OR ATMOSPHERE QUENCH RATE OF A MINIMUM 50 DEGREES F PER MINUTE DOWN TO 900°F IS
CRITICAL TO ACHIEVE BEST HEAT TREAT RESPONSE.

TEMPER IMMEDIATELY FOLLOWING QUENCH WHEN MATERIAL REACHES 150°F OR BELOW.

TEMPERING

MINIMUM 400°F TEMPERING TEMPERATURE REQUIRED.
DOUBLE TEMPERING IS REQUIRED, TRIPLE TEMPERING RECOMMENDED.
AIR COOL TO ROOM TEMPERATURE BETWEEN TEMPERS.

TYPICAL HEAT TREAT RESPONSE

TEMPERING TEMP		HARDENING	
°F	°C	TEMP	TEMP
		1775°F	970°C
As QUENCHED		63 HRC	
400	205	61 HRC	
500	260	60 HRC	
600	315	59 HRC	
700	371	58 HRC	
800	427	57 HRC	
900	480	56 HRC	
1000	538	56 HRC	
1100	552	50 HRC	